

TO: BILL TYLER

FAX 304-9834

FROM: NITOLD SOKOLOWSKI

MILITARY SPECIFICATION

GLASS BEADS: FOR CLEANING AND PEENING

M-29-13
MIL-G-9954A
Amendment 3
15 October 1987
Superseding
Amendment 2
30 Jan 80

LIG0-P960016-00-D
T960207

This amendment forms a part of Military Specification MIL-G-9954A dated 1 November 1966, and is approved for use by the Department of the Air Force and is available for use by all Departments and Agencies of the Department of Defense.

Page 1

Paragraph 2.1 - Under Specifications delete "Military, MIL-D-3464, Desiccants, Activated, Bagged, Packaging Use and Static Dehumidification".

Page 2

Paragraph 2.1 - Under Tech Manuals add "T.O. 1-1-2, Corrosion Prevention and Control for Aerospace Equipment".

Paragraph 2.1 - Under Technical Manuals delete "Air Force, TO 1-1-5, Abrasive Blasting Method of Cleaning and Corrosion Removal".

Paragraph 2.2 - Under American Society for Testing Materials Publications delete "C 169-69, Soda Lime Glass, Chemical Analysis of." and substitute "C169 Methods for Chemical Analysis of Soda-Lime and Borosilicate Glass."

Page 3

Paragraph 3.3 - After the word "Appearance" add "and Roundness". After the last sentence add the following sentence: "The roundness of the glass beads shall be specified in Table 1 for each size". (See 4.5.2)

* Paragraph 3.7 - Delete in its entirety, and substitute "Sieve analysis. The glass beads shall conform to the sieve analysis as specified in Table 1 when tested as specified. (See 4.5.6)"

Page 5

* Paragraph 4.3 - Delete the sentence "Each lot shall not exceed 2000 pounds" and substitute "Each lot shall not exceed 2000 pound consisting of 40 separate 50-pound containers."

FSC 5350

Distribution Statement A1 Approved for public release; distribution is unlimited.

THIS DOCUMENT CONTAINS 2 PAGES.

MIL-G-9954A
Amendment 3

Page 7

Paragraph 5.1.1 - Under sub-paragraph 1, delete "Type II and III, Grade X with dipped ends" and add "Type VI, Style B, MB-3, Sack No 13X, outer wall to be minimum of 50 LB basic weight".

Paragraph 5.1.1 - Sub-paragraph 4, delete in its entirety, and substitute the following: "When specified, five pounds of glass beads shall be placed in a plastic bag and the bag heat sealed. The vapor transmission rate of the plastic bag shall be as specified in paragraph 5.1.4. Ten 5-pound bags shall be packed for shipment in a 50-pound container as specified in 1, 2, or 3 above."

Paragraph 5.1.2 - Under sub-paragraph 1, delete "Type II or III, Grade L/W" and add "Type VI, Style B, MB-3, Sack No 13X, Outer Wall to be minimum of 50LB Basic weight".

Paragraph 5.1.2 - Add a new sub-paragraph 4 as follows: "When specified, five pounds of glass beads shall be placed in a plastic bag and the bag heat sealed. The vapor transmission rate of the plastic bag shall be as specified in paragraph 5.1.4. Ten 5-pound bags shall be packed for shipment in a 50-pound container as specified in 1, 2, or 3 above".

Page 8

Paragraph 5.1.4 - In the first sentence, delete the words "with a minimum of eight units of desiccant conforming to MIL-D-3464".

Paragraph 6.1 - In the fourth line, insert "Air Force" between "with" and "Technical", delete "1-1-5" and substitute "1-1-2".

* Paragraph 6.3 - In Line 10, delete "Warner Robins Air Material Area (WRAMA), ATTN: MMIRDA" and substitute "WR-ALC/MMIRFW".

"The margins of this amendment are marked with an asterisk to indicate where changes (additions, modifications, corrections, deletions) from the previous amendment were made. This was done as a convenience only and the Government assumes no liability whatsoever for any inaccuracies in these notations. Bidders and contractors are cautioned to evaluate the requirements of this document based on the entire content irrespective of the marginal notations and relationship to the last previous amendment".

Custodian:

Army - MR
Navy - AS
Air Force - 99

Preparing Activity
Air Force - 84

Project No:
5350-0009

Review Activities:

Army - AR
Navy - YD
DLA - IS
NASA - DS

User Activities:

Navy - CG

FSC 5350

2

M-29-13
MIL-G-9954A
1 NOVEMBER 1966
Superseding
MIL-A-9954 (USAF)
25 May 1962
MIL-A-22936 (WEP)
9 June 1961

MILITARY SPECIFICATION

GLASS BEADS: FOR CLEANING AND PEENING

This specification is mandatory for use by Departments and Agencies of the Department of Defense

1. SCOPE

1.1 Scope. This specification covers glass beads to be used with pressure/suction type blasting equipment.

1.2 Classification. Glass beads shall be of one type and 13 sizes as specified in Table I.

2. APPLICABLE DOCUMENTS

2.1 The following documents of the issue in effect on the date of invitation for bids, or request for proposal form a part of this specification to the extent specified herein.

SPECIFICATIONS

Federal

UU-S-48
PPP-C-96

PPP-D-723

Military

MIL-D-3464

Sacks, Shipping, Paper
Cans, Metal, 28 Gage and
Lighter
Drums, Fiber

Desiccants, Activated, Bagged,
Packaging Use and Static
Dehumidification

STANDARDS

Military

MIL-STD-105

Sampling Procedures and Tables for
Inspection by Attributes

NSG 5350

THIS DOCUMENT CONTAINS 9 PAGES.

MIL-G-9954A

MIL-STD-129

MIL-STD-147

MIL-STD-852 (USAF)

TECHNICAL MANUALS

Air Force

T.O. 1-1-5

Marking for Shipment and Storage
Palletized Unit Loads (40" X 48"
4-Way Partial and 4-Way Pallets)
Glass Bead Peening Procedures

Abrasive Blasting Method of
Cleaning and Corrosion Removal

(Copies of specifications, standards, drawings, and publications required by suppliers in connection with specific procurement functions should be obtained from the procuring activity or as directed by the contracting officer.)

2.2 Other publications. The following documents form a part of this specification to the extent specified herein. Unless otherwise indicated, the issue in effect on date of invitation for bids or request for proposal shall apply:

American Society for Testing
Materials Publications

C 169-65T

D 1214-58

Methods for Chemical Analysis of
Soda Lime Glass for Silicon Dioxide
Sieve Analysis of Glass Spheres

(ASTM Standards may be purchased from the American Society for Testing and Materials, 1916 Race Street, Philadelphia, Pennsylvania 19103.)

3. REQUIREMENTS

3.1 Qualification. The glass beads furnished under this specification shall be products which are qualified for listing on the applicable Qualified Products List at the time set for opening of bids. (See 4.2.1 and 6.3)

3.2 Composition. The glass beads shall be manufactured from a high grade, crown glass of the soda lime type. The glass beads shall contain not less than 62% silica. (See 4.5.1)

NOTE: THIS IS NOT FREE SILICA AND PRESENTS
NO HEALTH HAZARD DUE TO SILICOSIS.

MIL-G-9954A

3.3 Appearance. The glass beads shall be spherical, free flowing, free of defects, and free of foreign matter in accordance with high grade commercial practice. No more than 3% of any size shall be scored, broken or unfused angular glass particles. (See 4.5.2)

3.4 Coating. No silicone or trace of silicone coating will be permissible on the glass beads. (See 4.5.3)

3.5 Specific gravity. The specific gravity of the glass beads shall be not less than 2.3. (See 4.5.5)

3.6 Magnetic iron particles. No more than 0.1% by weight of free magnetic iron particles shall be permissible. (See 4.5.5)

3.7 Roundness. The roundness of the glass beads shall be as specified in Table I for each size. (See 4.5.2)

3.8 Sieve analysis. The glass beads shall conform to the sieve analysis as specified in Table I when tested as specified. (See 4.5.6)

4. QUALITY ASSURANCE PROVISIONS

4.1 Responsibility for inspection. Unless otherwise specified in the contract or purchase order, the supplier is responsible for the performance of all inspection requirements as specified herein. Except as otherwise specified, the supplier may utilize his own facilities or any commercial laboratory acceptable to the Government. The Government reserves the right to perform any of the inspections set forth in the specification where such inspections are deemed necessary to assure that supplies and services conform to prescribed requirements.

4.2 Classification of tests. The inspection and testing of glass beads shall be classified as follows:

a. Qualification tests. Qualification tests are those tests performed on samples submitted for approval of qualified products.

b. Quality Conformance tests. Quality conformance tests are those tests performed on individual lots which have been submitted for acceptance under contract.

4.2.1 Qualification tests. Qualification tests shall consist of all tests specified in this specification. (See 4.5)

4.2.2 Quality conformance tests. Quality conformance tests shall consist of the following tests:

- a. Sieve analysis (See 4.5.6).
- b. Magnetic iron particles (See 4.5.5).
- c. Appearance (See 4.5.2).

U. S. STD SCREEN	HEAD SIZE - $\frac{1}{2}$ ROUND, MIN. - $\frac{1}{2}$ PASSING												
	1	2	3	4	5	6	7	8	9	10	11	12	13
	60% Round	60% Round	65% Round	70% Round	70% Round	80% Round	80% Round	80% Round	80% Round	90% Round	90% Round	90% Round	95% Round
10	100												
12	95-100	100											
14	0-15	95-100	100										
20	0-5	0-15	95-100	100									
30		0-5	0-15	95-100	100								
40			0-5	0-15	95-100	100							
50				0-5	0-15	95-100	100						
60					0-5	0-15	95-100	100					
70						0-5	0-15	95-100	100				
80							0-5	0-15	95-100	100			
100								0-5	0-15	95-100	100		
120									0-5	0-15	95-100	100	
140										0-5	0-15	95-100	100
170											0-5	0-15	95-100
200												0-5	0-15
230													0-5
325													
400													

TABLE I

MIL-G-9951A

MIL-G-9954A 53 ■ 9999906 0099732 2 ■

STL BLDG #125 RM 112

4.3 Inspection Lot for Quality Conformance Test. For purposes of inspection, a lot shall consist of one size of glass beads manufactured at the same time and offered for delivery at one time. Each lot shall not exceed 2,000 pounds.

4.4 Sampling.

4.4.1 Sampling for quality conformance tests. Three containers shall be selected at random from each inspection lot. The material from each container shall be quartered or riffled by the method described in ASTM D 1214-58, paragraph 4, except that 500 grams of glass beads shall be used for tests. Each of the samples thus obtained shall be subjected to all of the prescribed tests. If more than one sample fails any test, the inspection lot shall be rejected.

4.5 Test methods.

4.5.1 Silica content. The silica content shall be determined in accordance with ASTM Method C 169-65T.

4.5.2 Scored, broken, unfused angular particles and roundness. These tests shall be made on three random samples as obtained in paragraph 4.4.1 and an actual count made of a field of approximately 100 beads. A microscope with a 20X magnification, substage lighting and a rule micrometer disc or slide, shall be used to make the count. The average count of each specimen shall be reported as percent true spheres.

4.5.3 Coating. The test for silicone coating on the glass beads shall be performed on three random samples obtained as specified in paragraph 4.4.1, as follows: slowly pour 50 grams of the glass beads into a 250 ml beaker containing 200 mls of distilled water. Any coagulation of the glass beads is an indication of silicone coating. The glass beads should disperse when poured into the water; however, a small number floating on the water is permissible.


4.5.4 Specific Gravity. A 60 gram sample of glass beads, previously dried, shall be placed in a 100 ml graduated cylinder containing 50 mls of distilled water. The total volume, minus 50, will give the volume of the beads. The specific gravity shall be computed as follows:

$$\text{Sp. Gr.} = \frac{\text{Weight of sample (grams)}}{\text{Water level (mls) after addition of sample} - 50 \text{ mls}}$$

4.5.5 Magnetic iron particles. Three samples obtained as specified in 4.4.1 shall each be sprinkled on an inclined magnetic plane (See Figure I) until no magnetic particles are retained on the inclined magnetic plane. After each sprinkling of the glass beads, carefully brush any magnetic particles into a tared weighing dish. When no more magnetic particles are visible on the magnetic plane, weigh the magnetic iron particles and compute the percentage.

MIL-G-9954A

FIGURE I

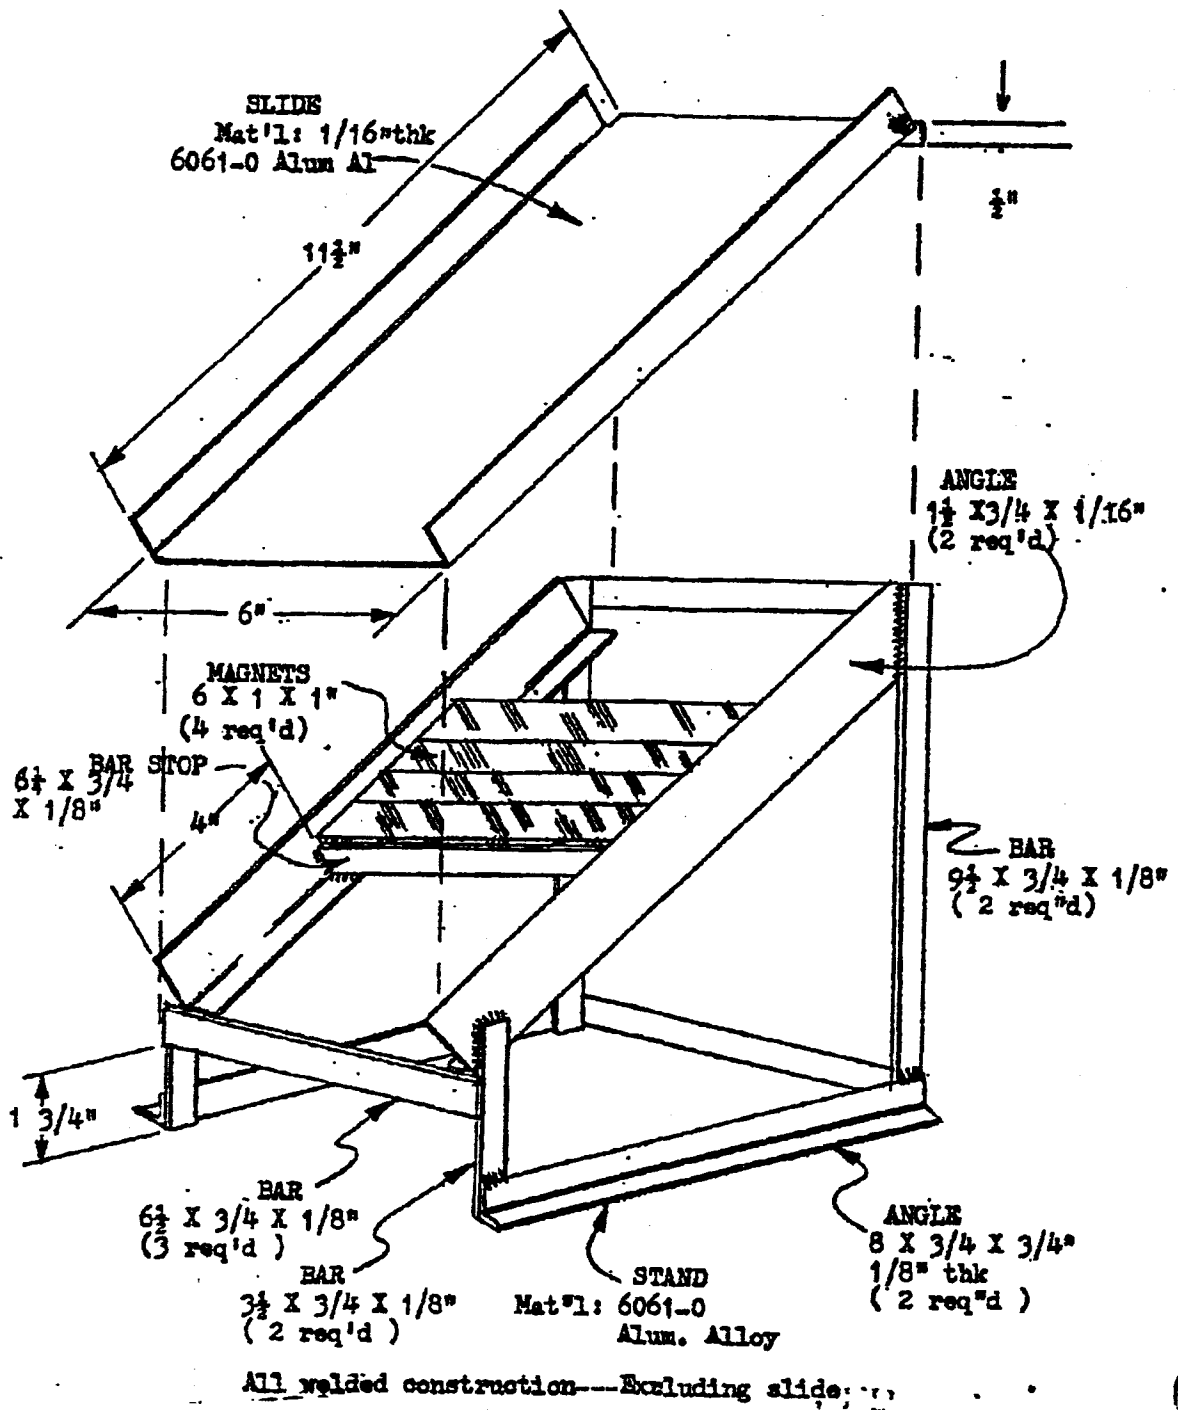

MIL-G-9954A 53 ■ 9999706 0099735 8 ■

MIL-G-9954A

4.5.6 Sieve Analysis. Samples as obtained in 4.4.1 shall be tested in accordance with ASTM Method D 1214-58, except that a 100 gram sample shall be used instead of a 50 gram sample.

4.5.7 Inspection of fill of containers and preparation for delivery. A random sample of filled containers shall be selected from each inspection lot in accordance with MIL-STD-105 at Inspection Level II and the AQL shall be 2.5% defective.

5. PREPARATION FOR DELIVERY

5.1 Packing and Palletizing. Packing shall be Level A, B or C, as specified. When specified, the containers for Level A or B shall be palletized in accordance with MIL-STD-147. When palletizing is specified for Level C, the pallet shall be the four way commercial expendable type.

5.1.1 Level A. The glass beads shall be packed for overseas shipment in 50 pound containers conforming to one of the following:

1. Multi-wall paper shipping sacks conforming to Federal Specification UU-S-48, Type II or III, Grade X with "dipped ends".
2. Fiber drums conforming to Federal Specification PPP-D-723, Type III.
3. Metal cans conforming to Federal Specification PPP-C-96.

4. Paper sacks, of the multi-wall, sewn open mouth type, constructed as follows: (a) A water resistant scrim of not less than two layers of 30 pound natural kraft, reinforced with glass fibers, and (b) not less than three layers of 50 pound natural kraft, and (c) one layer of 60 pound natural kraft. The scrim laminant shall be of asphalt or non-asphaltic material with a softening point of not less than 180° to 200°F. The lengthwise glass fibers of the scrim paper, shall be spaced not more than an average of $\frac{1}{2}$ inch apart and the crosswise fibers spaced not less than an average of two per inch; except when a diamond pattern is employed for crosswise reinforcement, the spacing between the parallel sides of the diamond shall average not more than one inch. The closing materials shall be tape, 12/6 cotton thread, paper filler cord with a pull tape feature.

5.1.2 Level B. The glass beads shall be shipped in 50 pound containers conforming to one of the following:

1. Multi-wall shipping sacks conforming to Federal Specification UU-S-48, Type II or III, Grade L/W.
2. Fiber drums conforming to Federal Specification PPP-D-723, Type I.
3. Metal cans conforming to Federal Specification PPP-C-96.

MIL-G-9954A 53 ■ 9999906 0099736 7 ■

MIL-G-9954A

5.1.3 Level C. The glass beads, in 50 pound containers, shall be shipped in accordance with the suppliers commercial practice in a manner to assure protection against damage during direct shipment from the supply source to the first receiving activity for immediate use. Shipping containers shall comply with the Uniform Freight Classification Rules, or regulations of other carriers as applicable to the mode of transportation.

5.1.4 Prior to packing in the above containers, the glass beads shall first be packaged in a plastic bag with a minimum of eight units of desiccant conforming to MIL-D-3464. The plastic bag shall have a minimum vapor transmission rate of less than 0.5 grams of water per 100 square inches per 24 hours. The mouth of these bags shall be twisted, doubled and wire tied.

5.2 Marking. Each container shall be marked in accordance with MIL-STD-129, and shall also be marked with the batch/grind and lot number.

6. NOTES.

6.1 Intended use. The glass beads covered by this specification are intended for use dry in suction/pressure blasting equipment to clean, peen, polish and finish ferrous and non-ferrous materials in accordance with Technical Manual T.O. 1-1-5, Military Standard MIL-STD-852 (USAF) and other government/industry documents.

6.2 Ordering data. Procurement documents should specify the following:

- a. Title, number, and date of this specification.
- b. Size desired.
- c. Quantity desired.
- d. Capacity of containers and type of container to be furnished.
- e. Selection of applicable levels of packaging and packing.

6.3 Qualification. With respect to products requiring qualification, awards will be made only for such products as have, prior to the time set for opening of bids, been tested and approved for inclusion in the applicable Qualified Products List, whether or not such products have actually been so listed by that date. The attention of the suppliers is called to this requirement, and manufacturers are urged to have their products that they propose to offer to the Federal Government tested for qualification in order that they may be eligible to be awarded contracts or orders for the products covered by this specification. The activity responsible for the Qualified Products List is the Warner Robins Air Materiel Area (WRAMA), Attn: WRNEG, Robins Air Force Base, Georgia 31093, and information pertaining to qualification of products may be obtained from this activity. (See 3.1 and 4.2.1).

MIL-G-9954A

Custodians:

- Army - MR
- Navy - AS
- Air Force - 84

Preparing Activity:

- Air Force - 84
- (Project No. 5350-0031)

Review Activities:

- Army - MR, WC
- Navy - AS, SC
- Air Force - 84

User Activities:

- Army -
- Navy - CG
- Air Force - , 71, 82

MIL-S-5002D (1)

9999906 1980514 952

NOT MEASUREMENT
SENSITIVE
MIL-S-5002D
AMENDMENT 1
24 March 1994

MILITARY SPECIFICATION
SURFACE TREATMENTS AND INORGANIC COATINGS
FOR METAL SURFACES OF WEAPONS SYSTEMS

This amendment forms a part of MIL-S-5002D, dated 30 November 1989,
and is approved for use by all Departments and Agencies
of the Department of Defense.

PAGE 1

2.1.1:

- a. Delete: "O-T-620 - Trichloroethane-1,1,1, Technical, Inhibited
(Methyl Chloroform)"
- b. Add: "O-T-634 - Trichloroethylene, Technical

PAGE 2

2.1.1:

- a. Delete:
"MIL-M-6874 - Metal Spraying, Process for
MIL-T-81533 - 1,1,1-Trichloroethane, (Methyl Chloroform),
Inhibited, Vapor Degreasing
MIL-P-83348 - Powder, Plasma Spray"
- b. Add:
"MIL-P-85856 - Powder Materials for Flame and Plasma
Sprayed Coatings"

PAGE 3

2.2. delete:

"ASTM D 3443 - Chloride in Trichlorotrifluoroethane"

AMSC N/A

AREA MFFP

DISTRIBUTION STATEMENT A. Approved for public release; distribution is unlimited.

1 of 2

MIL-S-5002) (3)

9999906 1980515 899

MIL-S-5002D
AMENDMENT I

PAGE 4

3.4.1:

a. line 8: After "O-T-236" delete: "1,1,1-trichloroethane conforming to MIL-T-81533 or O-T-620" and add: "trichloroethylene conforming to O-T-634"

b. line 16: After "aliphatic" delete: "petroleums" and add: "hydrocarbons"

3.4.1.1, line 3: After "for" delete: "1,1,1-trichloroethane" and add: "trichloroethylene"

PAGE 6

3.4.3, delete last 2 sentences in paragraph and substitute: "The completeness of flux removal shall be determined in accordance with the applicable welding, soldering or brazing specification."

PAGE 7

3.5.1.2.1, line 3: After "MIL-C-8837" delete: ", or thermal spray coated in accordance with MIL-M-6874"

PAGE 9

3.5.1.21, line 7: Delete "MIL-P-83348" and substitute: "MIL-P-85856"

PAGE 13

4.3.2, delete in entirety.

PAGE 14

6.11, Key Word List, add: "Trichloroethylene"

Custodians:

Army - MR
Navy - AS
Air Force - 11

Preparing activity:
Navy - AS

(Project MFFP-0226)

Review activities:

Army - AR, AV, EA, MI
Navy - OS
Air Force - 99
DLA-ES

MIL-S-5002D MF ■ 9999906 0420417 1 ■

H-11-13

NOT MEASUREMENT SENSITIVE
MIL-S-5002D
30 November 1989
SUPERSEDING
MIL-S-5002C
26 July 1971

MILITARY SPECIFICATION

SURFACE TREATMENTS AND INORGANIC COATINGS
FOR METAL SURFACES OF WEAPONS SYSTEMS

This specification is approved for use by all Departments and Agencies of the Department of Defense.

1. SCOPE

1.1 Scope. This specification covers the requirements for cleaning, surface treatments and inorganic coatings for metallic surfaces of weapons systems parts.

2. APPLICABLE DOCUMENTS

2.1 Government documents.

2.1.1 Specifications, standards, and handbooks. The following specifications, standards, and handbooks form a part of this specification to the extent specified herein. Unless otherwise specified, the issues of these documents shall be those listed in the issue of the Department of Defense Index of Specifications and Standards (DODISS) and supplement thereto, cited in the solicitation.

SPECIFICATIONS

FEDERAL

- O-A-51 - Acetone, Technical.
- O-T-236 - Tetrachloroethylene (Perchloroethylene), Technical Grade.
- O-T-620 - Trichloroethane-1,1,1, Technical, Inhibited (Methyl Chloroform)
- P-D-680 - Dry Cleaning Solvent
- QQ-C-320 - Chromium Plating (Electrodeposited).

Beneficial comments (recommendations, additions, deletions) and any pertinent data which may be of use in improving this document should be addressed to: Systems Engineering and Standardization Department (Code 53), Naval Air Engineering Center, Lakehurst, NJ 08733-5700, by using the self-addressed Standardization Document Improvement Proposal (DD Form 1426) appearing at the end of this document or by letter.

AMSC N/A

AREA MFFP

DISTRIBUTION STATEMENT A. Approved for public release; distribution is unlimited.

THIS DOCUMENT CONTAINS 14 PAGES.

- QQ-N-290 - Nickel Plating (Electrodeposited).
- QQ-P-35 - Passivation Treatments for Corrosion Resisting Steel.
- QQ-P-416 - Plating, Cadmium (Electrodeposited).
- QQ-S-365 - Silver Plating, Electrodeposited, General Requirements for.
- TT-N-95 - Naphtha, Aliphatic.
- MILITARY**
- MIL-M-3171 - Magnesium Alloy, Processes for Pretreatment and Prevention of Corrosion on.
- MIL-C-5541 - Chemical Conversion Coatings on Aluminum Alloys.
- MIL-M-6874 - Metal Spraying, Process for.
- MIL-F-7179 - Finishes, Coatings, and Sealants for the Protection of Aerospace Weapons Systems.
- MIL-A-8625 - Anodic Coatings, for Aluminum and Aluminum Alloys.
- MIL-C-8837 - Coating, Cadmium (Vacuum Deposited).
- MIL-T-10727 - Tin Plating, Electrodeposited or Hot-dipped, for Ferrous and Nonferrous Metals.
- MIL-S-13165 - Shot-Peening of Metal Parts.
- MIL-C-14550 - Copper Plating (Electrodeposited).
- DOD-P-16232 - Phosphate Coating, Heavy, Manganese or Zinc Base (for Ferrous Metals).
- MIL-C-17711 - Coatings, Chromate, for Zinc Alloy Castings and Hot Dip Galvanized Surfaces.
- MIL-P-18317 - Plating, Black Nickel (Electrodeposited) on Brass, Bronze, or Steel.
- MIL-C-23217 - Coating, Aluminum, Vacuum Deposited.
- MIL-P-23408 - Plating, Tin-Cadmium (Electrodeposited).
- MIL-C-26074 - Coating, Electroless Nickel, Requirements for Magnesium Alloy, Anodic Treatment of.
- MIL-M-45202 - Gold Plating, Electrodeposited.
- MIL-G-45204 - Palladium Plating (Electrodeposited).
- MIL-P-45209 - Rhodium Plating, Electrodeposited.
- MIL-R-46085 - 1,1,1 Trichloroethane (Methyl Chloroform), Inhibited; Vapor Degreasing.
- MIL-T-81533 - Coating, Cadmium, Tin-Cadmium and Zinc (Mechanically Deposited).
- MIL-C-81562 - Zirconium Oxide, Line-stabilized, Powder and Rod, for Flame Spraying.
- MIL-Z-81572 - Plating, Tin-Lead (Electrodeposited).
- MIL-P-81728 - Coating, Aluminum and Aluminum Alloys (Metallic Compound Decomposition).
- MIL-C-81740 - Coating, Metallic-Ceramic.
- MIL-C-81751 - Coating, Inorganically Bonded Aluminum (Electrophoretically Deposited).
- MIL-C-81797 - Powder, Plasma Spray.
- MIL-P-83348 - Coating, Aluminum, Ion Vapor Deposited.
- MIL-C-83488 - Chromium-Molybdenum Plating (Electrodeposited).
- MIL-C-85455 - Chromium-Molybdenum Plating (Electrodeposited).

MIL-S-5002D MF MIL-S-5002D 9999906 0420419 5

STANDARDS

MILITARY

- MIL-STD-865 - Selective (Brush Plating) Electrodeposition
- MIL-STD-870 - Cadmium Plating, Low Embrittlement, Electrodeposition
- MIL-STD-889 - Dissimilar Metals.
- MIL-STD-1500 - Cadmium-Titanium Plating, Low Embrittlement, Electrodeposition

(Copies of specifications and standards can be obtained from the Naval Publications and Forms Center, (Attn:NPODS), 5801 Tabor Avenue, Philadelphia, PA 19120-5099.)

2.2 Other publications. The following documents form a part of this specification to the extent specified herein. Unless otherwise specified, the issues of the documents which are DOD adopted shall be those listed in the issue of the DODISS specified in the solicitation. Unless otherwise specified, the issues of documents not listed in the DODISS shall be the issue of the nongovernment documents which is current on the date of the solicitation.

- AMERICAN SOCIETY FOR TESTING AND MATERIALS (ASTM)
 - ASTM B 600 - Recommended Practices For Descaling And Cleaning Titanium And Titanium Alloy Surfaces.
 - ASTM B 633 - Electrodeposited Coatings of Zinc on Iron and Steel.
 - ASTM D 2942 - Total Acid Acceptance of Halogenated Organic Solvents (Nonreflux Methods)
 - ASTM D 3443 - Chloride In Trichlorotrifluoroethane.

(Applications for copies should be addressed to the American Society for Testing and Materials, 1916 Race Street, Philadelphia, PA 19103.)

- SOCIETY OF AUTOMOTIVE ENGINEERS (SAE)
 - AMS 2416 - Plating - Nickel-Cadmium, Diffused.
 - AMS 2424 - Plating - Nickel, Low Stressed Deposit

(Applications for copies should be addressed to the Society Of Automotive Engineers, 400 Commonwealth Drive, Warrendale, PA 15096.)

2.3 Order of precedence. In the event of a conflict between the text of this specification and the references cited herein (except for associated detail specifications, specification sheets or MS standards), the text of this specification shall take precedence. Nothing in this specification, however, shall supersede applicable laws and regulations unless a specific exemption has been obtained.

3. REQUIREMENTS

3.1 Materials and processes. Materials and processes shall conform to applicable documents, as specified herein. Materials and processes not covered by applicable specifications shall not be used unless approved by the cognizant engineering organization.

3.2 Finishing requirements. Unless otherwise specified, all fabrication operations, including thermal treatments and cleaning, shall have been completed prior to application of any surface treatment, metallic coating, and/or non-metallic coating.

MIL-S-5002D MF ■ 9999906 0420420 1 ■

MIL-S-5002D

3.3 Surfaces. Parts, with the exception of those processed in accordance with DOD-P-16232, shall conform to specified dimensions and surface roughness conditions after final cleaning, surface treatment or coating. In the case of metals which may respond in a non-uniform manner when metal removal is done with mechanical, chemical, electrochemical, or electromechanical methods, appropriate inspection procedures shall be established and used to ensure each part has a uniform surface, including freedom from pits and intergranular attack. Where etching results, the degree found shall be demonstrated not to affect the serviceability of the parts.

3.4 Cleaning. Cleaning, prior to application of surface treatments and coatings, shall be as specified herein. These methods shall be utilized in a manner which does not result in damage to the metal, including freedom from pits, intergranular attack, and hydrogen embrittlement. When specified, an appropriate hydrogen embrittlement relief test shall be conducted. After cleaning, all parts shall be completely free of corrosion products, scale, paint, grease, oil, flux (see 3.4.3), and other foreign materials including other metals. After cleaning, the parts shall be coated as soon as practicable. Particular care shall be exercised in the handling of parts to assure that foreign metals are not inadvertently transferred, as may occur when steel is allowed to come into contact with zinc surfaces. In addition, assemblies containing either parts under sustained tensile stresses or crevices which may retain cleaning solutions shall not be cleaned as assemblies.

3.4.1 Organic contamination removal. Organic soils shall be removed by emulsion cleaning, alkaline or electrolytic alkaline cleaning (anodic only), solvent immersion, solvent spraying, vapor degreasing (see 3.4.1.2), solvent hand cleaning, or combinations thereof, whichever is more applicable to the nature of the part and soil to be removed. The materials and processes used shall be completely characterized and controlled to ensure no corrosion effects. Vapor degreasing shall be performed using either perchloroethylene conforming to O-T-236, or 1,1,1 trichloroethane conforming to MIL-T-81533 or O-T-620. When vapor degreasing is utilized, the condensate of each vapor degreasing unit shall be tested for acidity at least once each month, as dictated by history and usage, to determine conformance with 3.4.1.1. If an acid condition exists, the use of the vapor degreasing unit shall be discontinued until the acid condition is corrected and available treated parts shall be 100 percent inspected for corrosion effects. Parts displaying corrosion effects shall be subject to rejection. Hand cleaning shall be performed using the solvents mentioned above or aliphatic petroleum such as naphtha conforming to TT-N-95, or acetone conforming to O-A-51. Solvent hand cleaning shall be performed using a lint free cloth. Residues from the cleaning agents shall be thoroughly rinsed off.

3.4.1.1 Acid acceptance. When tested in accordance with 4.3.1, The total acid acceptance as equivalent NaOH in weight percent shall be .01 percent or above for perchloroethylene and .03 percent or above for 1,1,1-trichloroethane.

3.4.1.2 Titanium and Titanium alloys. Organic contamination removal from titanium and titanium alloys shall be as specified in 3.4.1 but subject to the following limitations. Assembled titanium parts shall not be vapor degreased. Unassembled titanium parts may be vapor degreased if followed by an acid or alkaline dip. The time of vapor degreasing shall be the minimum to effect removal without causing damage.

MIL-S-5002D MF ■ 9999906 0420421 3 ■
MIL-S-5002D

3.4.2 Inorganic contamination (scale) removal. Inorganic contamination removal (descaling) shall be performed as specified herein. If specified by the cognizant engineering organization, parts shall be stress relieved prior to chemical or electrochemical methods of descaling to remove residual tensile stresses.

3.4.2.1 Aluminum and its alloys. Aluminum and its alloys shall be either chemically, (see 6.4), or mechanically cleaned except as specified herein. Mechanical cleaning using abrasives containing iron and its oxides, steel wool and wire, and copper alloy based materials, which may become embedded and accelerate corrosion of aluminum alloys, shall not be used.

3.4.2.2 High strength steels. Steels, including corrosion and heat resistant steels, hardened by thermal treatment or by cold working to full or surface hardness level of Rockwell C40(180 KSI) and higher, shall be cleaned using either mechanical means, alkaline or electrolytic alkaline descaling (anodic only), molten salt bath methods or, when necessary, acid pickling. Acid pickling shall be followed by a 2 hour bake at a temperature of $375 \pm 25^\circ\text{F}$ ($190 \pm 15^\circ\text{C}$) prior to the coating operation, see 6.5.

3.4.2.3 Low-strength steels. Steels of Rockwell hardness less than C40(180 KSI) shall be cleaned using either mechanical means, alkaline or electrolytic alkaline descaling, molten salt bath methods, acid pickling, or combinations thereof. Immersion times in the pickling bath shall be kept at a minimum such that hydrogen absorption is prevented.

3.4.2.4 Corrosion and heat resisting steels. Corrosion and heat resisting steels having a Rockwell Hardness less than C40(180 KSI) shall be cleaned by suitable chemical or mechanical processes, or combinations thereof as specified in 3.4.2.3. However, high strength corrosion and heat resisting steels, C40(180 KSI) and above, shall be cleaned as specified in 3.4.2.2. For metals and alloys which are sensitive to contamination by gaseous constituents, such as hydrogen, oxygen, and nitrogen, and are exposed to atmospheres containing such materials during heat treatment, etc., sufficient metal shall be removed during manufacture to eliminate the contaminated material (see 3.2). Verification that the procedures used to provide complete elimination of contaminated material shall be documented. Where chemical cleaning methods are used to remove the impurities, the materials shall not result in any attack of the surface, either pitting or intergranular. Weekly determination for this behavior shall be made using a microscopic method and examined at a magnification which will clearly establish the condition. Parts with pitted surfaces or showing intergranular attack shall be subject to rejection.

3.4.2.4.1 Passivation treatment. 200, 300, 400 series and precipitation-hardened corrosion resistant steels shall undergo passivation in accordance with QQ-P-35, or by other methods approved by the cognizant engineering organization, see 3.1 and 6.7. Passivation shall be followed by a thorough rinsing and drying. Carburized or nitrided surfaces shall not be subjected to passivation. Passivation is not required for corrosion resistant steels which are to be inorganically coated, or abrasively cleaned for the purpose of painting.

3.4.2.5 Magnesium and its alloys. Magnesium and its alloys shall be cleaned in accordance with MIL-M-3171.

MIL-S-5002D MF

MIL-S-5002D.

9999906 0420422 5

3.4.2.6 Titanium and its alloys. For removal of contamination other than organic soil, (see 3.4.1.2), titanium and its alloys shall be cleaned in accordance with ASTM B 600.

3.4.3 Flux removal. Soldering, welding, and brazing fluxes shall be removed by the use of hot water, soap and water, alcohol, dry cleaning solvents conforming to P-D-680 (Type II), or other appropriate methods that do not result in attack of the metal. Methyl alcohol shall not be used on magnesium or titanium and their alloys. Acid or alkaline materials shall not be used, unless approved by the cognizant engineering organization. Flux removal effectiveness shall be such that no more than 13 ppm of chloride ion is present when tested in accordance with 4.3.2. If non-chloride containing fluxes are used, an appropriate test method shall be developed and used subject to approval of the cognizant engineering organization, see 3.1.

3.4.4 Use of abrasives. Abrasives used on any metal or alloy shall not have been used on other metals or alloys unless they were used for a similar base metal (for example, aluminum alloys), or it can be demonstrated that the suppliers' recycling process eliminates damaging contaminants.

3.4.5 Rinsing. When either acid or alkaline materials are employed, the cleaned parts shall be given a thorough rinse with water of adequate purity to remove all acid or alkali prior to the coating operation, such that no residual contamination remains.

3.5 Coatings.

3.5.1 Metallic coatings.

3.5.1.1 Methods of application. Metallic coatings shall be applied by electrodeposition, vacuum deposition, mechanical deposition, metallic compound deposition, thermal spraying methods, hot dip methods, or ion vapor deposition, in conformance to applicable specifications. If specifically approved by the cognizant engineering organization, brush plating in accordance with MIL-STD-865 may be used where conventional plating methods are inappropriate, see 6.8. Unless otherwise specified in the applicable plating specification, electrodeposited coatings shall not be used on steel parts having a surface hardness of Rockwell C49 (240 Ksi) or above unless approval is obtained from the cognizant engineering organization. Where coatings are applied thermally, in no case shall the part be raised to a temperature which would adversely affect its mechanical, corrosion or stress corrosion resistant properties. If a part is shot-peened prior to the coating application, all thermal treatments performed after shot peening shall conform to the requirements of MIL-S-13165.

3.5.1.2 Cadmium coatings. Electrodeposited cadmium shall be in accordance with QQ-P-416 or MIL-STD-870, see 3.5.4. Other cadmium coatings shall be in accordance with MIL-C-8837, MIL-C-81562, or thermal spray coated in accordance with MIL-M-6874. Unless otherwise specified, cadmium coatings shall be Class 1 thickness (0.0005 inch). Parts with threads shall be plated to Class 2 thickness (0.0003 inch). Cadmium coatings shall not be used for the following applications:

- a. Parts which may be in contact with hydraulic fluids, fuels, lubricating oil, and other petroleum based fluids.
- b. Parts in frictional contact where gouging or binding may be a detrimental factor.

MIL-S-5002D MF MIL-S-5002D 9999906 0420423 7

- c. In confined spaces, in the presence of organic materials which give off corrosive or damaging vapors.
- d. On titanium parts or fasteners. In addition, cadmium plated parts such as interference-fit fasteners or press-fit bushings shall not be used in contact with titanium, see 6.9.
- e. Parts which will be subsequently soldered.
- f. Components which will come into contact with graphite composites.
- g. Parts that will be exposed to temperatures above 450°F (232°C),

3.5.1.2.1 Parts containing recesses or entrapments. Parts containing recesses or entrapments which may retain cleaning and plating fluids shall be vacuum coated in accordance with MIL-C-8837, or thermal spray coated in accordance with MIL-M-6874. Additional protection, such as an organic coating system, may be required for recesses that cannot be coated by these methods.

3.5.1.3 Cadmium-titanium plating. Cadmium-titanium plating shall be in accordance with MIL-STD-1500.

3.5.1.4 Nickel-cadmium plating. Nickel-cadmium plating shall be in accordance with AMS 2416, (see 3.5.4).

3.5.1.5 Tin-cadmium coatings. Electrodeposited Tin-cadmium shall be in accordance with MIL-P-23408. Other tin-cadmium coatings shall be in accordance with MIL-C-81562.

3.5.1.6 Tin and tin-lead plating. A plating of tin or tin-lead may be used on parts which are subsequently soldered. Tin plating shall be applied in accordance with MIL-T-10727 and tin-lead plating shall be in accordance with MIL-P-81728, (see 3.5.4).

3.5.1.7 Aluminum coating. Aluminum and aluminum alloy coatings shall be used where the properties of these materials present distinct protective advantages in comparison with other coatings and platings at temperatures in excess of 450°F. Aluminum and aluminum alloy coatings are also used for corrosion resistance and galvanic compatibility, see 3.5.4. Aluminum and aluminum alloy coatings shall be in accordance with MIL-C-81740, MIL-C-23217, or MIL-C-83488. Unless otherwise specified, surface treatment of aluminum and aluminum alloy coatings, when required, shall be as specified in 3.5.3.1.

3.5.1.8 Zinc plating and coating. Zinc plating shall be in accordance with ASTM B 633 and zinc coating shall be as specified in MIL-C-81562 (see 3.5.4). Unless otherwise specified, zinc plating or coating shall have a minimum thickness of 0.001 inch. Zinc plating and coating shall not be used for the following applications:

- a. Parts for aerospace and missile systems.
- b. Parts in contact where corrosion products might interfere with normal functioning.
- c. Grounding contacts where the increased electrical resistance of zinc-plated surfaces would be objectionable.

MIL-S-5002D MF ■ 9999906 0420424 9 ■
MIL-S-5002D

3.5.1.8.1 Chromate treatment. Zinc plated or coated parts, specified for a Type II finish, shall be given a supplementary chromate conversion coating in accordance with MIL-C-17711.

3.5.1.9 Chromium plating. Chromium plating shall be used for all surfaces subject to wear or abrasion, except where other surface hardening processes, such as nitriding or carburizing are used, or where other wear and abrasion resistant coatings are specified. Chromium plating shall be in accordance with QQ-C-320, Class 2 (engineering), with a minimum thickness of 0.002 inch, unless otherwise specified. If a Class 1 (corrosion) coating is specified, and the part will not be subjected to lubricants during use, a nickel undercoat shall be applied in accordance with QQ-N-290 having a minimum thickness of 0.0015 inch. When chromium plating is specified, it shall be used on only one of two contacting surfaces.

3.5.1.10 Nickel plating. Except when used as an undercoating, see 3.5.5, electrodeposited nickel shall be in accordance with QQ-N-290, Class 2 (engineering) with a minimum thickness of 0.002 inch, unless otherwise specified. Nickel plating shall be used for the following applications only:

- a. Where temperatures do not exceed 1,000°F (538°C) and other coatings would not be suitable.
- b. To minimize the effects of crevice corrosion with unplated corrosion-resisting steel or stainless steel in contact with other stainless steel.
- c. As an undercoat for other functional coatings (see 3.5.5).
- d. To restore dimensions by rebuilding worn surfaces.
- e. For resistance to sand erosion.

3.5.1.10.1 Low residual stress. Where applications require low residual stress in the plated nickel, plating shall be in accordance with AMS 2424 .

3.5.1.11 Silver plating. Silver plating shall be in accordance with QQ-S-365. Silver plating shall not be used on titanium or in contact with titanium, see 3.5.6, for parts which are used at temperatures above 550°F (289°C) in service, see 6.10. Silver shall not be used with nickel base alloys above 1000°F (538°C). When electrodeposited silver is used on steel, an underplate of either copper or nickel, or combinations of both shall be applied. Unless otherwise specified by the cognizant engineering organization, the underplate and the silver plate shall each have a minimum thickness 0.0005 inch, yielding a 0.001 inch minimum total thickness.

3.5.1.12 Gold plating. Gold plating shall be in accordance with MIL-G-45204.

3.5.1.13 Palladium plating. Palladium plating shall be in accordance with MIL-P-45209.

3.5.1.14 Rhodium plating. Rhodium plating shall be in accordance with MIL-R-46085.

MIL-S-5002D MF ■ 7999906 0420425 0 ■

MIL-S-5002D

3.5.1.15 Black nickel plating. Black nickel plating shall be in accordance with MIL-P-18317.

3.5.1.16 Copper plating. Copper plating shall be in accordance with MIL-C-14550.

3.5.1.17 Hot-dip coatings. Hot-dip coatings may be used within the limitations prescribed herein for the same coating materials applied by other methods where specifically approved by the cognizant engineering organization. Hot dip tin coatings shall be in accordance with MIL-T-10727.

3.5.1.18 Electroless nickel coating. Electroless nickel coatings shall be in accordance with MIL-C-26074. When electroless nickel is used for corrosion protection or wear resistance, the minimum thickness shall be 0.0015 inch and the maximum thickness shall not exceed 0.003 inch, unless otherwise specified by the cognizant engineering organization.

3.5.1.19 Zirconium oxide coating. Zirconium oxide coating shall be processed from materials in accordance with MIL-Z-81572.

3.5.1.20 Chromium-molybdenum plating. Chromium-molybdenum plating shall be in accordance with MIL-C-85455.

3.5.1.21 Thermal spraying. Assemblies which will trap plating solutions and assemblies or parts which are of extreme size and weight for conventionally available plating or coating equipment shall be thermal sprayed. The material for coating shall be applied directly to the surface of the part after suitable surface preparation. Unless otherwise specified, the coating thickness shall be 0.004 to 0.006 inch. Powders which are to be used for plasma spray coatings shall conform to MIL-P-83348.

3.5.1.21.1 For corrosion control (see 3.5.4). When metallic materials, such as zinc or aluminum are thermal sprayed for corrosion control of parts, no undercoating of another metal such as molybdenum shall be permitted as the substrate.

3.5.1.21.2 For functional purposes (see 3.5.5). When non-metallic coatings, such as zirconia, alumina, metallic-ceramics (MIL-C-81751), carbides, silicides, titanates, cermets, etc., are thermal sprayed for functional use on parts, an undercoat of another material or mixtures of materials in various proportions to produce coatings shall be allowed as a substrate where required to control the matching of the coefficients of thermal expansion of the base metal and the coating.

3.5.2 Ceramic-metallic and ceramic coatings.

3.5.2.1 Methods of application. Metallic-ceramic and ceramic coatings shall be applied by spraying, dipping, electrophoretic deposition, or thermal spraying methods in conformance with applicable specifications, followed by a fusion or mechanical treatment, if applicable. Where thermal application processes are used, in no case shall the part be subjected to a temperature that would adversely affect its mechanical, corrosion, or stress corrosion properties. If the part is shot-peened prior to coating, the thermal application shall not impair the effectiveness of the shot-peening operation.

MIL-S-5002D MF ■ 999906 0420426 2 ■

MIL-S-5002D

3.5.2.2 Metallic-ceramic coating. Metallic-ceramic coatings are to be used for surfaces subject to oxidation, corrosion, galvanic corrosion, and for protection from corrosion due to other environments, (see 3.5.4). Metallic-ceramic coatings shall be in accordance with MIL-C-81751 or MIL-C-81797.

3.5.3 Surface treatments and oxide coatings.

3.5.3.1 Aluminum and aluminum alloys. Unless otherwise specified, all aluminum and aluminum alloys, including clad aluminum alloy surfaces, shall be either anodized to produce coatings conforming to MIL-A-8625 or shall receive a chemical conversion treatment to produce coatings conforming to MIL-C-5541. Parts subject to wear, abrasion, erosion, and severe corrosion condition shall be anodized.

3.5.3.1.1 Aircraft applications. All non-clad aluminum and aluminum alloys used in exterior locations of aircraft which are classified as exterior surfaces by MIL-F-7179 shall be anodized to produce coatings complying with the requirements of MIL-A-8625.

3.5.3.1.2 Electrical parts. Chemical films conforming to Class 3 treatment of MIL-C-5541 shall be used on electrical parts where low electrical contact resistance is required. Other surface treatments for low electrical resistance and corrosion protection may be used when approved by the cognizant engineering organization.

3.5.3.1.3 Hard anodic coatings for aluminum and its alloys. Hard anodic coatings shall conform to Type III of MIL-A-8625. They shall be used on parts where the functional purpose is to provide a wear resistant surface. It should be noted that hard anodic coatings have a detrimental effect on the fatigue life of aluminum alloys.

3.5.3.2 Magnesium and magnesium alloys.

3.5.3.2.1 Method. All magnesium alloys shall be anodized in accordance with MIL-M-45202, Type I, Class A or Class C, or Type II, Class A or Class D. MIL-M-3171 treatments shall only be used for temporary protection or touch-up of damaged anodic coatings, see 3.5.3.2.2.

3.5.3.2.2 Touch-up. All surfaces which have the anodic or chemical film removed or damaged shall be touched up, using either the Type I or Type VI process of MIL-M-3171. Magnesium surfaces, anodic coated in accordance with MIL-M-45202, may be stripped and re-anodized when approved by the cognizant engineering organization.

3.5.3.3 Phosphate coatings. Phosphate treatments, when approved by the cognizant engineering organization, may be used on surfaces where it is impractical to apply an adequate corrosion control coating or where a corrosion control coating will interfere with the parts function. When approved for use on steel parts, phosphate treatments shall be in accordance with DOD-P-16232.

3.5.3.4 Surface treatments for corrosion and heat-resisting steel alloys. Unplated corrosion-resisting and heat-resisting steel alloys shall be finished as specified.

MIL-S-5002D MF ■ 999906 0420427 4 ■

MIL-S-5002D

3.5.4 Coatings for corrosion control of steels and copper based parts. Unless otherwise specified, steels and copper base parts shall be cadmium, nickel-cadmium, tin-cadmium, tin-lead, tin, aluminum (steel parts only), zinc, nickel, or metallic-ceramic coated. (see 3.5.1.2 thru 3.5.1.8, 3.5.1.10, and 3.5.2.2).

3.5.4.1 Exceptions. Unless otherwise specified, the following exceptions apply:

3.5.4.1.1 Corrosion resistant materials. Coatings may be omitted from corrosion and stress corrosion resistant materials, except for the following conditions:

- a. Where the intended use is such that added protection is warranted.
- b. Where parts of these materials are in contact with dissimilar metals as defined in MIL-STD-889.
- c. Where unsealed crevices exist either within the part or the assembly of which it may be a component, or in contact with wood.

3.5.4.1.2 Sintered bearings. Sintered bearings of the oil-impregnated type shall not be plated. Crevices between the bearing and the housing shall be sealed if the two constitute a dissimilar metal as defined in MIL-STD-889.

3.5.4.1.3 Non-corrosion resistant metal parts. All non-corrosion resistant metal parts used for components of lubricating and hydraulic systems and components exposed to lubricants or hydraulic fluids, except for tubing, shall be tin-cadmium plated in accordance with MIL-P-23408. Alternative protective systems may be used subject to the approval of the cognizant engineering organization.

3.5.5 Coatings for functional purposes. Coatings for functional purposes shall be as specified in 3.5.1.9, 3.5.1.11 through 3.5.1.16, and 3.5.1.18 through 3.5.1.20. Unless otherwise specified, where the selected coating does not provide corrosion protection for the base metal and the coated surface or portion thereof is exposed to corrosive environment, an undercoat of 0.0010 to 0.0016 inch of nickel on steel or zinc parts or an undercoat of 0.0008 to 0.0010 inch of nickel on copper alloy parts in accordance with QQ-N-290 or AMS 2424 shall be used. Coatings proposed for applications where temperatures exceed 1,000°F (538°C) in service shall be subject to approval by the cognizant engineering organization.

MIL-S-5002D MF ■ 999906 0420428 6 ■
MIL-S-5002D

3.5.6 Temperature limitations. Unless otherwise specified, the temperature of the coated parts, items in direct contact with the coated parts, or, when erosive conditions exist, surrounding parts which may be contacted by eroded coating particles shall not exceed the following:

Silver	1,200°F	1/
Nickel	1,000°F	
Metallic ceramic	950°F	2/
Aluminum	925°F	2/
Zinc	500°F	
Cadmium	450°F	3/
Tin-lead	350°F	4/
Tin-cadmium	345°F	4/
Tin	330°F	4/

1/ Shall not be used on titanium parts or in contact with titanium parts exposed to temperatures over 550 deg.F in service (see 3.5.1.11).

2/ Above 950°F there may be an unfavorable effect upon the fatigue strength of the steel base metal due to diffusion.

3/ See 3.5.1.2 (d).

4/ Pure tin or tin containing materials which undergo a solid-state transformation, shall not be used for parts which are for use at subzero temperatures.

3.6 Shot-peening and other residual compressive stress-inducing treatments. Shot-peening, in accordance with MIL-S-13165, and other compressive stress-inducing treatments shall be used to obtain improved fatigue behavior and stress corrosion cracking resistance, using controlled procedures. The maximum temperatures for use on any part shall not exceed 50°F less than the recovery temperature of the stressed surface of the material involved. Procedure details shall be prepared and listed on the applicable drawings or applicable reference documents for parts. Specific attention shall be paid to use of recognized procedures, equipment, materials, and control methods.

3.7 Workmanship. Parts and assemblies shall be the result of use of the best processes covered herein, as demonstrated by serviceability of the parts.

4. QUALITY ASSURANCE PROVISIONS

4.1 Responsibility for inspection. Unless otherwise specified in the contract or purchase order, the contractor is responsible for the performance of all inspection requirements as specified herein. Except as otherwise specified in the contract or purchase order, the contractor may use his own or any other facilities suitable for the performance of the inspection requirements specified herein, unless disapproved by the Government. The Government reserves the right to perform any of the inspections set forth in the specification where such inspections are deemed necessary to assure supplies and services conform to prescribed requirements.

MIL-S-5002D MF ■ 9999906 0420429 8 ■
MIL-S-5002D

4.1.1 Responsibility for compliance. All items must meet all requirements of section 3. The inspection set forth in this specification shall become a part of the contractor's overall inspection system or quality program. The absence of any inspection requirements in the specification shall not relieve the contractor of the responsibility of assuring that all products or supplies submitted to the Government for acceptance comply with all requirements of the contract. Sampling in quality conformance does not authorize submission of known defective material, either indicated or actual, nor does it commit the Government to acceptance of defective material.

4.2 Inspection. The methods of cleaning metal surfaces, application of surface treatments, and all materials entering into the processes shall be subject to inspection. When inspection is conducted at the contractor's plant, all required tests shall be done by the contractor.

4.2.1 Previous approval. Acceptance or approval of material or of any surface treatment or corrosion preventive process during the course of manufacture shall, in no case, be construed as a guarantee of the acceptance of the finished product.

4.3 Test methods.

4.3.1 Acid acceptance test. Determination of acid acceptance as equivalent NaOH weight percent shall be conducted in accordance with ASTM D 2942.

4.3.2 Flux removal. Welded, soldered, or brazed areas shall be tested for completeness of flux removal by leaching the area with a small quantity of distilled water. To the leachate, add a few drops of nitric acid and a few drops of 5 percent silver nitrite solution. If a white precipitate is formed in an amount greater than that formed in an equal volume of standard sodium chloride solution (equivalent to 13 ppm as chloride) treated in the same manner, flux removal is not complete.

5. PACKAGING

This section is not applicable to this specification.

6. NOTES

6.1 Intended use. The surface treatments and coatings prescribed by this specification are intended for use on metal surfaces of aerospace weapons, electrical, electronic and other systems.

6.2 Ordering data.

This section is not applicable to this specification.

6.3 Definitions. The terms "coating" and "plating" as used in this document may be used interchangeably. However, the term "coating" is generally applied to materials on metal surfaces deposited by nonelectrodeposition processes, whereas "platings" are those materials deposited electrolytically.

MIL-S-5002D MF ■ 9999906 0420430 4 ■

MIL-S-5002D

6.4 Aluminum Cleaners. Cleaners conforming to MIL-M-7752, MIL-C-43616, or MIL-C-87936 are recommended for cleaning aluminum parts, (see 3.4.2.1).

6.5 Effects of the embrittlement bake. For several steel types, a thin oxide layer may be formed after the two hour bake which may result in poor coating adhesion.

6.6 Cognizant engineering organization. The cognizant engineering organization is the term applied to the engineering organization responsible for the design of the item being cleaned and coated.

6.7 Passivation. A passive film can be obtained by embedding steel grit into the surface of a part and then applying a phosphate coating in accordance with DOD-P-16232. Note that this procedure becomes less effective for parts having high rockwell hardness values due to the difficulty of embedding the steel grit. This method may be useful on 400 series and cast CRES alloys which are inherently difficult to passivate.

6.8 Brush plated chrome. Brush plated chrome coatings have substantially lower hardness values than conventionally plated chrome coatings. This will result in a lower abrasion resistance.

6.9 Liquid metal embrittlement. Under certain conditions, titanium can be embrittled by contacting cadmium or silver components. Embrittlement has been determined to occur in cadmium plated titanium parts at temperatures as low as 150°F, and in silver brazed titanium parts at temperatures above 600°F.

6.10 Changes from previous issue. Asterisks are not used in this revision to identify changes with respect to the previous issue due to the extensiveness of the changes.

6.11 Key word listing. The following subject terms (key words) are listed to allow identification of this document during retrieval searches:

Coatings
Inorganic Coatings
Surface Treatments
Weapons Systems

Custodians:
Army - MR
Navy - AS
Air Force - 11

Preparing activity:
Navy - AS

(Project MFFP-0226)

Review activities:
Army - AR, AV, EA, MI
Navy - OS
Air Force - 99

User activities:
DLA-ES